

Accepted Article Preview: Published ahead of advance online publication**Scalable, ultra-resistant structural colors based on network metamaterials**

Henning Galinski, Gael Favraud, Hao Dong, Juan S Toterogongora, Grégory Favaro, Max Döbeli, Ralph Spolenak, Andrea Fratalocchi and Federico Capasso

Cite this article as: Henning Galinski, Gael Favraud, Hao Dong, Juan S Toterogongora, Grégory Favaro, Max Döbeli, Ralph Spolenak, Andrea Fratalocchi and Federico Capasso. Scalable, ultra-resistant structural colors based on network metamaterials. *Light: Science & Applications* accepted article preview 27 September 2016; doi: 10.1038/lsa.2016.233.

This is a PDF file of an unedited peer-reviewed manuscript that has been accepted for publication. NPG are providing this early version of the manuscript as a service to our customers. The manuscript will undergo copyediting, typesetting and a proof review before it is published in its final form. Please note that during the production process errors may be discovered which could affect the content, and all legal disclaimers apply.

Received 19 April 2016; revised 20 September 2016; accepted 25 September 2016;
Accepted article preview online 27 September 2016

Scalable, ultra-resistant structural colors based on network metamaterials

Henning Galinski^{1,2,‡}, Gael Favraud^{3,‡}, Hao Dong^{1,2}, Juan S. Toterogongora³, Grégory Favaro⁴, Max Döbeli⁵, Ralph Spolenak², Andrea Fratolocchi^{3,*} and Federico Capasso^{1,‡}

¹*John A. Paulson School of Engineering and Applied Sciences, Harvard University, Cambridge 02138, USA*

²*Laboratory for Nanometallurgy, ETH Zurich, Vladimir-Prelog-Weg 1-5/10, Zurich, Switzerland*

³*PRIMALIGHT, King Abdullah University of Science and Technology (KAUST), Thuwal 23955-6900, Saudi Arabia*

⁴*Anton Paar TriTec SA, CH-2034 Peseux, Switzerland*

⁵*Ion Beam Physics, ETH Zurich, Otto-Stern-Weg 5, Zurich, Switzerland*

(Dated: April 17, 2016)

Running title: Scalable, ultra-resistant structural colors

Abstract

Structural colors have drawn wide attention for their potential as a future printing technology for various applications, ranging from biomimetic tissues to adaptive camouflage materials. However, an efficient approach to realize robust colors with a scalable fabrication technique is still lacking, hampering the realization of practical applications with this platform. Here, we develop a new approach based on large-scale network metamaterials that combine dealloyed subwavelength structures at the nanoscale with lossless, ultra-thin dielectric coatings. By using theory and experiments, we show how subwavelength dielectric coatings control a mechanism of resonant light coupling with epsilon-near-zero (ENZ) regions generated in the metallic network, generating the formation of saturated structural colors that cover a wide portion of the spectrum. Ellipsometry measurements support the efficient observation of these colors, even at angles of 70 degrees. The network-like architecture of these nanomaterials allows for high mechanical resistance, which is quantified in a series of nano-scratch tests. With such remarkable properties, these metastructures represent a robust design technology for real-world, large-scale commercial applications.

Keywords: nanophotonics; plasmonics; structural colors

[‡]capasso@seas.harvard.edu, ^{*}andrea.fratolocchi@kaust.edu.sa (CFO) These authors contributed equally to the work. rights reserved.

INTRODUCTION

Billions of years ago, green algae originated life, changing the face of the earth from gray to green and paving the way for the life forms we see today ¹. Since then, living organisms have extensively used color for a variety of purposes, ranging from communication to self-defense, from reproduction to camouflage ². The enormous variety of colors, such as the sapphire blue wings of the Morpho butterfly ^{3, 4} and the thermochromic coloration of the chameleon ⁵, has stimulated the interest of researchers dating back to the 17th century, when Hooke theorized about the origin of color in the brilliant feathers of peacocks and ducks ⁶. Many of these colors do not originate from pigments or dyes but are ‘structural’, resulting from the interaction of light with self-assembled structures of living organisms ^{4, 7, 8}.

The engineering of structural colors from artificial photonic structures has attracted conspicuous interest in research due to the many applications that can potentially be opened by this technology ^{5, 9–17}. Structural colors based on photonic crystals and metamaterials have been explored, showing very promising results, including the possibility to create colors at the diffraction limit ¹⁵. A major challenge is overcoming the problems of limited scalability and lack of robustness, which affect the real-world applicability of photonic crystals and classical metamaterials. It is therefore highly desirable to investigate new approaches that can transform these initial breakthroughs into real world applications.

In the following, we describe a new biomimetic material that overcomes the aforementioned challenges, introducing a new type of structural coloration that is highly scalable and extremely robust. This nanomaterial takes inspiration from subwavelength nanoscale networks identified in the feathers of *Cotinga maynana*, a South American bird ¹⁸. The non-iridescent blue color of the feathers is produced by an aperiodic nanoporous keratin network with a typical feature size smaller than 200 nm. This lightweight network has extraordinary optical properties that cannot be explained by classical Rayleigh/Mie scattering and are strongly related to the short-range order of the nano-network of the barbs ¹⁹. The interaction of light waves with complex materials has already been reported to have a series of fascinating dynamics, ranging from energy harvesting to ultra-dark nanomaterials and beyond ^{7, 11, 20–27}. Taking inspiration from the *Cotinga maynana* feathers as an example in nature of a network-based optical nanomaterial, we create complex nano-photonic structures that combine a cellular metallic network ^{28, 29} with subwavelength

coatings made by lossless dielectrics. This material combination provides significant advantages for real world applications: it is suited for large-scale fabrication and is lightweight and mechanically robust, combining the high yield strength to low density ratio of a cellular metallic network with the resistance to wear that alumina offers³⁰. Optically, the interface of such a metallic nanoscale network and the lossless dielectric can be considered as electromagnetically “weakly” rough and an inhomogeneous mixture of dielectric/metal and dielectric/air regions. In this scenario, the component of the wavevector parallel to the interface is not conserved, resulting in a highly spatially dependent electromagnetic response. Taking advantage of such a complex light-matter interaction, we illustrate here how to create colors with remarkable properties.

MATERIALS AND METHODS

Sample Preparation and Characterization

PtYAl layers of 300 nm thickness were deposited at room temperature by magnetron co-sputtering onto SiN_x/Si substrates that were pre-cleaned using isopropanol and acetone. Subsequently, the films were dealloyed in 4 M NaOH at room temperature for 60 s and then rinsed with deionized water. The morphological analysis of the samples was studied via scanning electron microscopy (SEM) assisted by focused ion beam etching (FIB). The compositional analysis was performed by Rutherford backscattering spectrometry. Detailed information is given in the Supplementary Information. In this work, the Savannah atomic layer deposition (ALD) from Ultratech/Cambridge NanoTech (Waltham, Massachusetts, USA) was used to deposit Al₂O₃ coatings on the dealloyed metal nanowire networks. During the ALD deposition of Al₂O₃, a pulse time of 0.15 s and a purge time of 30 s for both TMA and water were used. The base pressure was 500 mTorr, and the working temperature was 250°C. The growth rate was approximately 0.1 nm per cycle. For creating colored graphic arts, the 60 nm thick Al₂O₃ film was deposited via radio frequency (RF) sputtering at room temperature using a sputtering tool (AJA International, Scituate, MA, USA). The electromagnetic reflectance of the coated samples was measured using a variable-angle spectroscopic ellipsometer from J.A. Woollam Co (Lincoln, NE, USA) and a NanoCalc thin film reflectometry setup (Ocean Optics Inc.,

Dunedin, FL, USA). The dielectric constant of the Al_2O_3 coating deposited by ALD was determined using a Cauchy model by analyzing a 53 nm thick Al_2O_3 coating deposited on a Si wafer. The scratch tests were performed using an Anton Paar TriTec Nano Scratch Tester (Anton Paar TriTec SA, Peseux, Switzerland).

Finite-Difference Time-Domain (FDTD) simulations.

Numerical simulations were carried out using our parallel code NANOCPP, which is a highly scalable (up to hundreds of thousands CPU) Maxwell equation solver, able to include dispersive materials with arbitrary dispersion curves²⁰. To build a realistic model for our sample, we considered a metallic structure whose profile was extracted from the morphological analysis of the samples (FIB) shown in Fig. 1a. The dispersion parameters of the various materials were taken from direct measurements. Light impinging on the sample was simulated within the Transmitted Field/Scattered Field formulation²⁰, which allows the detailed modelling of plane wave input excitations on the samples.

RESULTS AND DISCUSSION

Material design and color characterization

We selected dealloying to assemble a nanoscale metallic network with controllable features. This method, first proposed by Raney to synthesize metal catalysts³¹, utilizes the selective dissolution of the less noble constituent of an alloy during wet etching. In our experiments, 300 nm thick $\text{Pt}_{14}\text{Y}_{0.06}\text{Al}_{1.80}$ thin films were deposited on an amorphous $\text{Si}_3\text{N}_4/\text{Si}$ substrate. While immersing the film in a 4 M aqueous solution of NaOH for 60 s, the less noble Al in the Pt-alloy thin film is subsequently removed, and the remaining metal reorganizes into a network with an open porosity. Characteristic geometrical features of the network can be altered by changing the etching time, the etchant concentration or the initial composition of the thin film^{32–36}.

In a second step, the nanomaterial is coated with an ultra-thin layer of Al_2O_3 using ALD. The coating thickness is increased stepwise in a range from 7 to 53 nm. We characterized the growth of the subwavelength Al_2O_3 coatings by Rutherford backscattering spectroscopy and

FIB assisted SEM (see Supplementary Information). A three-dimensional image of the Pt₅₆Y₂₆Al₁₈ network, experimentally obtained using FIB thin film tomography, is displayed in Fig. 1a.

In a final series of experiments, we characterized the optical response of the network metamaterial for different thicknesses of the dielectric layer Al₂O₃. These experiments unveiled a very interesting mechanism of structural coloration from the nanowire network, as shown in Fig. 1b. By changing the coating thickness, we observed the formation of a multitude of colors spanning from yellow, orange, and red to, finally, blue. The same physical effect with the optical response blue-shifted and smaller color range was observed for a Pt-Al network (see Supplementary Information and Supplementary Fig. S 9). Conversely, when the same coatings were deposited on a dense PtYAl metal thin film, no particular color was produced (see Supplementary Information and Supplementary Fig. S 5). The colors observed in the metallic network were saturated and go even slightly beyond the Red Green Blue (RGB) gamut in the CIE chromaticity diagram (Fig. 1c).

To illustrate that these colors were consistently observed by varying Al₂O₃ layer thickness, we compared experimental results with theoretical predictions based on Finite Difference Time-Domain (FDTD) simulations. For the latter, we used a 2D section of the FIB tomography of the sample illustrated in Fig. 1a. Our FDTD simulations, shown in Fig. 1c as a dotted line, reproduced the experimental results well, confirming the possibility of achieving such a large variety of colors by tuning the thickness of the Al₂O₃ layer. Figure 1b shows experimental images of samples characterized by different thicknesses of Al₂O₃. Remarkably, despite the existence of the metallic nanoscale network below the Al₂O₃ layer, the samples demonstrated a highly uniform color in all different configurations. A comparison with FDTD calculations is provided in Fig. 1d, which illustrates the color palette that can be observed when the thickness of Al₂O₃ increases.

To emphasize that the structural coloration in these nanoplasmonic structures can be achieved by various deposition techniques, we also fabricated a structural colored graphic arts by using physical vapor deposition. Figure 2 depicts an example created by combining a dealloyed network metamaterial with an RF-sputtered 60 nm thick Al₂O₃ coating and photolithography using a Heidelberg μ PG501 optical direct writing system. The bicolored graphic art combines a highly uniform structural color (blue) with a metallic white color (dense film). The material

choice for the coating layer is not limited to Al_2O_3 a lossless dielectric. Dielectric coatings with and without losses could, in principle, be used to alter the plasmonic response and finally change the structural coloration. Another approach to altering the color impression, especially its saturation, is to change the number of trapping sites within the network metamaterial, for example, by reducing the metamaterial thickness.

Robustness of structural colors from metamaterial networks

To quantify the mechanical robustness of these colors, we resort to nano-scratch resistance testing (Fig. 3a), which is an ideal technique to characterize the adhesion failure of coatings. A detailed description of the experimental procedure we used is given in the supplemental material. Figure 3b reports optical micrographs of four representative nano-scratch tests. The wear resistance of a dense PtYAl film with and without a 28 nm thick Al_2O_3 coating is compared to a porous nanoscale Pt network coated with 28 nm and 53 nm of Al_2O_3 , respectively. The critical load causing delamination of the coated network metamaterial is almost 2 times higher than the corresponding dense metallic film (Fig. 2b) and 20% higher than the dense metallic film coated with 28 nm thick Al_2O_3 . Considering the 53% porosity in the nanoscale network, the observed increase in wear resistance is remarkable and indicates an enhanced strength-to-density ratio³⁷ corresponding to a significant reduction of overall weight of the coating. Figure 4 illustrates s-polarized reflectivity spectra at normal (Fig. 4a) and oblique (Fig. 4b-e) incidence for different alumina coating thickness. Figure 4a demonstrates that the formation of colors originates from a large red shift of the reflectivity response of the nanomaterial, observed when the Al_2O_3 layer changes thickness. The corresponding FDTD results are reported in Fig. 4f. FDTD simulations quantitatively reproduce well the experimental results, confirming the principal role of the Al_2O_3 coating layer in red-shifting the spectral response of the material. A small variation of only 30 nm in the Al_2O_3 thickness shifts the reflectivity minimum of approximately 350 nm. Reflectivity spectra of the material are stable and do not show significant variations up to incident angles of 70° , which still provide reflectivity minima as low as $< 1\%$ (Fig. 4b-e). The mean angular dispersion of the reflectance minimum has been determined from the reflectance spectra obtained by ellipsometry. The mean angular dispersion is independent of the coating thickness and the reflectance minimum blue

shifts with $-1.0 \pm 0.3 \text{ nm}/^\circ$. These experiments show that the structural colors observed in Fig. 1 are non-iridescent, that is, robust against large changes of the incident angle.

Structural coloration from localized surface states in complex epsilon-near-zero (ENZ) materials

In this section, we analyze in more detail the mechanisms by which structural colors are created and observed in the metallic network of Fig. 1. When polychromatic light impinges on the structure of Fig. 1a, the interaction between light and matter generates surface plasmon polaritons (SPP)³⁸, which are surface waves localized at the metal-dielectric interface of the structure⁷. In our samples (Fig. 5a), the motion of SPP develops along complex trajectories in space due to a strongly disordered metallic profile, (Fig. 5a, inset). It is convenient to study this motion in a new curvilinear system, whose axes are parallel to the spatial trajectories of SPP. To this extent, we introduce a new set of coordinates, (ψ, ϕ) , which are conformal to the disordered surface of the metal. Figure 5a shows how these coordinates appear in the original space, (x, y) , whereas Fig. 5b shows how the original structure appears in the space (ψ, ϕ) , which we identify as the ‘plasmonic reference.’ In the plasmonic reference, the motion of the surface plasmons is extremely simple and composed of straight lines at $\psi = 0$ (Fig. 5b, inset). When we change spatial coordinates in any electromagnetic system, Maxwell equations remain invariant if we introduce an inhomogeneous refractive index distribution that makes the two reference systems equivalent^{39, 40}. The pseudocolor plot in Fig. 5b shows the spatial distribution of the inhomogeneous index, $n(\psi, \phi)$, computed by using transformation optics (see Supplementary Information). The index, $n(\psi, \phi)$, is associated with the coordinate transformation introduced in Fig. 5b and acts as a counterpart of the metallic geometry of Fig. 5a, which does not exist in Fig. 5b, as the metal surface is flattened out. The two structures of Fig. 5a and Fig. 5b are exactly equivalent: when light propagates in one or another, it follows the same dynamics. This is an exact result of Maxwell equations that contains no approximation. This result also implies that when light impinges on the structure of Fig. 5a, it happens to propagate in the medium of Fig. 5b. The calculation of a conformal grid for the disordered surface of Fig. 5a requires a new formulation of optical

conformal mapping, which we recently developed, and allows for the generation of conformal grids for arbitrary structures with arbitrary-large numerical precision. This approach is relatively involved, and it will be discussed in a future work.

The plasmonic reference of Fig. 5b illustrates in clear form the effects of disorder, which introduce a strong modulation of the refractive index in the proximity of the metallic surface at $\psi = 0$, generating a network of epsilon-near-zero (ENZ) regions, separated by areas of high refractive index (Fig. 5b). As observed in the insets of Fig. 5a and Fig. 5b (dashed lines), ENZ regions are created in the points where the metallic surface is convex, whereas high dielectric permittivities originate in the points where the surface is concave. When waves propagate into an ENZ material, the phase velocity diverges, thus creating standing waves with infinite wavelengths^{41–43}. When SPP waves propagate in the nanowire network of Fig. 5a, they ‘see’ the equivalent medium illustrated in Fig. 5b and become trapped in the ENZ regions, thereby generating a set of quasi-localized states. We illustrated these dynamics by a series of FDTD simulations. Figure 6a presents a magnified version of Fig. 4a, showing FDTD-calculated reflectivity spectra for different thicknesses of the Al₂O₃ layer. FDTD results corresponding to different combinations of alumina thicknesses and input wavelengths are summarized in Figs. 6b–l. When light impinges on the disordered metallic structure (Fig. 6b), some energy is scattered back, generating components along all directions in space, whereas the remainder is coupled into SPP waves. As illustrated in Figs. 6c–e, which show FDTD-calculated electromagnetic energy density distributions, SPP waves are completely localized in the proximity of different convex points of the surface, exactly where the ENZ regions are formed. FDTD simulations show that different wavelengths are trapped in different ENZ regions of the metal, demonstrating that the ENZ network formed in Fig. 5b does not possess a particular length scale and that it traps equivalently all input wavelengths. The absence of a characteristic scale is expected from the strongly disordered surface modulation of the sample, which possesses an abundant variety of different curvatures (Fig. 5a) and therefore of ENZ regions with different extensions (Fig. 5b). The combinations of all of these ENZ regions traps polychromatic light very efficiently, as observed from the flat reflectivity response of Fig. 6a (solid green line). To further characterize the energy propagation in the structure, we also plotted the flow of electromagnetic energy in the structure, computed from the Poynting vector of the electromagnetic field (Fig. 6f). This is represented with a specific line integral convolution (LIC) technique, which clearly visualizes the energy flow, characterized by complex patterns with a nontrivial vorticity.

When we deposited a small layer of Al_2O_3 on top of the metal, the scattering dynamics changed abruptly (Fig. 6g). In this situation, a portion of scattered wavevectors were reflected inside the alumina layer, thus generating a series of additional scattering events in the Al_2O_3 . Wavevectors propagating at an angle, θ , (see Fig. 6g) larger than the critical angle, $\theta_c = \arcsin\left(\frac{n_{\text{AIR}}}{n_{\text{Al}_2\text{O}_3}}\right)$, formed by the interface of air and alumina were totally reflected back and do not radiate energy outside the alumina, surviving the dynamics for many scattering events. These components existed at any given thickness of alumina, as the critical angle depends only on the difference in the refractive index between alumina and air. Reflected wavevectors create a flow of energy in the layer of Al_2O_3 , inducing a preferential localization of SPP inside ENZ regions that exists within the film of Al_2O_3 . This process is clearly illustrated in Figs. 6h-i, which show the presence of a resonant coupling around the wavelength of 425 nm (Fig. 6l). Resonant light localization in ENZ regions within the alumina layer is observed in Fig. 6i, which demonstrates light trapping at the wavelength of 425 nm at different points of convex metallic curvature located inside the Al_2O_3 . Figure 6h-i and supplementary Fig. S7 show electromagnetic energy distributions calculated from the resonance, demonstrating that outside the reflectivity minimum located around the wavelength of 450 nm, no surface localization is formed, and no energy is trapped in the alumina layer. Figure 6m presents LIC images of the Poynting flux clearly showing the flux of energy originated inside the Al_2O_3 , from the light backscattered from the random metallic surface of the sample. By using arguments from wave theory and scale invariance of Maxwell equations (see Supplementary Information), we obtained a simple relationship for the wavelength shift, $\Delta\lambda(\Delta d)$, as a function of the thickness variation of alumina, $\Delta\lambda$,

$$\Delta\lambda = \frac{\lambda_0}{d_0} \Delta d, \quad (1)$$

where λ_0 is the wavelength of a reflectivity minimum corresponding to a coating thickness, d_0 . Figure 6n compares experimental measures with the results of Eq. (1). By applying experimental values for both λ_0 and d_0 , we obtained a coefficient $\lambda_0/d_0 \cong 12$, which implies a wavelength shift of 12 nm for every 1 nm increment of coating thickness. The results of Eq. (1) show a good agreement with experimental results, predicting the large red shift that is

the basis of the structural colors formed in the system.

CONCLUSIONS

We have experimentally demonstrated a new design concept to create robust and saturated structural colors in metasurfaces composed of metallic nanowire networks with ultra-thin, lossless dielectric coatings. Using a combination of analytical and numerical techniques, we illustrated that these colors are the result of the resonant coupling of light with surface plasmons that are localized in equivalent epsilon-near-zero regions formed in the metallic network. This mechanism is not constrained for large angles as high as 70° , allowing for efficient trapping of light over a broad wavelength range in the visible region. The combination of mechanical robustness and color saturation in an extremely lightweight structure makes these structural colors suitable for real world industrial applications, such as automotive vehicles or airplanes, for which the weight is directly related to the fuel economy. As discussed in the introduction, achieving a scalable fabrication is a key problem in structural color printing. On the basis of our experiments, it is evident that our metasurfaces have shown a wide color capability without the need for electron beam lithography (EBL) or other complex fabrication procedures. Our structures, in fact, are based on simple wet-chemistry and coating technologies, which can produce robust colors on large spatial scales. In addition to such fundamental advances, our design concept has the potential to enrich the application of metasurfaces to areas in which large active regions are mandatory, such as efficient light trapping layers in photovoltaic cells. Although a deeper discussion of this topic is beyond the scope of this paper, we can introduce some important points. On the basis of our theory and experiments, we demonstrated that it is possible to control the response of an optical material by ‘engineering’ the connectivity of a network of ENZ nanostructures created in a random metallic structure. From the results of Fig. 6, we observed that this approach allows for strong localization of optical radiation in nanoscale regions located well outside the metal, completely absorbing incoming optical photons in a specific bandwidth (Fig. 6l-m). This approach can potentially enhance the absorption power of ultra-thin absorbers, which can take advantage of the formation of localized spots and harvest a significant portion of light energy in nm-thick film structures. The current photovoltaic technology employs Si absorbers of approximatively $100\ \mu\text{m}$ thickness, whereas other solution-processed materials with high

manufacturability and low cost, such as quantum dots, require film thickness larger than 1 μm to efficiently absorb all incoming photons. Our metastructures can considerably scale down these thicknesses, stimulating new research aimed at developing innovative materials for renewable energy harvesting.

Acknowledgments

For computing, we used the resources of the KAUST Supercomputing Laboratory and the Redragon cluster of the Primalight group.

F Capasso acknowledges the Air Force Office of Scientific Research (MURI: FA9550-14-1-0389) for financial support. Part of the nano-fabrication was performed at the Center for Nanoscale Systems (CNS), a member of the National Nanotechnology Coordinated Infrastructure (NNCI), which is supported by the National Science Foundation under NSF award no. 1541959. CNS is part of Harvard University.

A Fratalocchi thanks P Magistretti for fruitful discussions on brain functions. A Fratalocchi acknowledges financial support from KAUST (Award CRG-1-2012-FRA-005).

H Galinski acknowledges the financial support of the 'Size matters' project (TDA Capital Ltd, London, UK). H Dong acknowledges the financial support by the Master Thesis Grant of 19 the Zeno Karl Schindler Foundation (Switzerland).

FIGURE LEGENDS

Fig. 1. Observation of structural colors in random metallic networks with subwavelength dielectric coatings. (a) Schematic illustration of an Al_2O_3 coated PtYAl nanomaterial, based on a 3D reconstruction of a completely dealloyed PtYAl thin film obtained via FIB assisted thin film tomography. (b) Photographs of deposited, dealloyed, and Al_2O_3 coated PtYAl metamaterial networks, illustrating the formation of vibrant colors and the continuous color change with increasing coating thickness. The photographs were taken under illumination from ceiling lights. Each image is $2 \times 2 \text{ mm}^2$. (c) Experimental and FDTD simulated structural color reported in a standard CIE 1931 (x, y) space, depicting the

chromaticity visible to the average person. The RGB color space is marked by the triangle area. The chromaticity is calculated directly from reflectance spectra obtained either experimentally (circles markers) or by FDTD simulations (dashed line). The edges of the tongue-shaped plane correspond to color values of maximal saturation. d, Color palette calculated by FDTD simulations for increasing thickness of Al_2O_3 .

Fig. 2. Examples of different graphic arts designs with structural colors from metamaterial networks. Photograph and optical micrograph of a colored graphic art designed by combining a RF-sputtered Al_2O_3 coated network metamaterial and photolithography. The inset shows an optical micrograph illustrating a detail of the graphic art and the uniformity of the color.

Fig. 3. Wear properties of the structural colors. (a) Schematic illustration of the basic principle of the scratch testing technique. A diamond stylus is used to scratch the film with progressively increasing load. (b) Optical micrographs of progressive load scratches (0.4–15 mN) on a dense PtYAl thin film with and without coating, and PtYAl nanoscale networks coated with 28 and 53 nm thick Al_2O_3 , respectively. The critical load characterizing the adhesion failure of the films is indicated by a pink arrow.

Fig. 4. Optical properties of the network metamaterials: reflectivity spectra. (a) Experimental normal incidence reflectance spectra as a function of the Al_2O_3 coating thickness, d . (b-e) Experimental reflectance spectra of nanoporous PtYAl thin films coated with 18 nm, 28 nm, 45 nm, and 53 nm Al_2O_3 , respectively, as a function of the incidence angle (20° – 85°). The value of reflectance is indicated by the color bar. (f) FDTD-calculated normal incidence reflectance spectra as function of the Al_2O_3 coating thickness, d .

Fig. 5. Generation of an equivalent ENZ material in the metallic nanowire network of Fig. 1a. (a) 2D cross section profile of the metallic nanowire network, as obtained from experimental FIB images of polished samples (Fig. 1a). When light impinges on this structure, it excites the propagation of surface plasmon polariton waves (SPP), which move along the complex surface of the metal (Panel a, inset). This motion is conveniently described in a

curvilinear reference (φ, ψ) , which provides a conformal map of the metallic surface of the sample (solid red line). In the transformed space, (φ, ψ) (panel b), SPP waves appear to propagate inside an inhomogeneous material with refractive index, $n(\varphi, \psi)$, on the line at $\psi=0$ (c, inset). The material, $n(\varphi, \psi)$, models the effects of the metallic geometry of panel (a), which is flattened out in transformed space, (φ, ψ) . The two systems of panels (a-b) are exactly the same for light propagation. The equivalent structure of (b) demonstrates a complex network of ENZ structures (panel b, dark blue area), which are created by points of convex metallic curvature (right inset).

Fig. 6. Mechanisms of structural color formation in the PtYAl cellular network. (a) Normal incidence reflectance spectra obtained from FDTD simulations of the nanoscale Pt network of Fig. 1a with different thickness of Al_2O_3 . Panels (b-f) analyze the case with no Al_2O_3 deposited on top of the metal, while panels (g-m) summarize the results for an Al_2O_3 layer of 33 nm. Panels (b,g) provide a pictorial illustration of light-matter interactions with the sample, without (b) and with (g) Al_2O_3 . In the presence of Al_2O_3 , a portion of scattered waves are reflected back in the Al_2O_3 layer, thus creating an energy flow in the coating layer and a resonant coupling with ENZ regions located in the Al_2O_3 . Panels (c-e) and (h-l) present FDTD-calculated spatial energy distributions in the structure by considering an input wavelength indicated by the corresponding letter in panel (a). Energy distributions are averaged over one optical cycle at steady state. Panel (f,m), conversely, provides a zoomed view of the pink area of panel (e,l) and illustrates the electromagnetic energy flow in the structure (arrow colored lines). The flow is superimposed with the corresponding averaged spatial energy distribution. Panel (n), finally, compares the reflectivity minimum shift observed in experiments (Fig. 4) with theoretical predictions based on the model illustrated in panel (g).

1 Yoon HS, Hackett JD, Ciniglia C, Pinto G, Bhattacharya D. A molecular timeline for the origin of photosynthetic eukaryotes. *Mol Biol Evol* 2004; **21**: 809-818.

2 Bradbury JW, Vehrencamp SL. *Principles of Animal Communication*. 2nd edn. Sunderland: Sinauer Associates, Inc.; 2011.

3 Potyailo RA, Ghiradella H, Vertiatchikh A, Dovidenko K, Cournoyer JR *et al.* *Morpho*

butterfly wing scales demonstrate highly selective vapour response. *Nat Photonics* 2007; **1**: 123-128.

4 Kinoshita S, Yoshioka S, Miyazaki J. Physics of structural colors. *Rep Prog Phys* 2008; **71**: 076401.

5 Teyssier J, Saenko SV, van der Marel D, Milinkovitch MC. Photonic crystals cause active colour change in chameleons. *Nat Commun* 2015; **6**: 6368.

6 Hooke R. *Micrographia: or Some Physiological Descriptions of Minute Bodies Made by Magnifying Glasses with Observations and Inquiries Thereupon*. New York: Cosimo Classics; 2007.

7 Huang JF, Liu CX, Zhu YH, Masala S, Alarousu E *et al*. Harnessing structural darkness in the visible and infrared wavelengths for a new source of light. *Nat Nanotechnol* 2016; **11**: 60-66.

8 Vukusic P, Hallam B, Noyes J. Brilliant whiteness in ultrathin beetle scales. *Science* 2007; **315**: 348.

9 Seago AE, Brady P, Vigneron JP, Schultz TD. Gold bugs and beyond: a review of iridescence and structural colour mechanisms in beetles (Coleoptera). *J R Soc Interface* 2009; **6**: S165-S184.

10 Kats MA, Blanchard R, Genevet P, Capasso F. Nanometre optical coatings based on strong interference effects in highly absorbing media. *Nat Mater* 2013; **12**: 20-24.

11 Kats MA, Sharma D, Lin J, Genevet P, Blanchard R *et al*. Ultra-thin perfect absorber employing a tunable phase change material. *Appl Phys Lett* 2012; **101**: 221101.

12 Schlich FF, Spolenak R. Strong interference in ultrathin semiconducting layers on a wide variety of substrate materials. *Appl Phys Lett* 2013; **103**: 213112.

13 Zhang YF, Dong BQ, Chen A, Liu XH, Shi L *et al*. Using cuttlefish ink as an additive to produce non-iridescent structural colors of high color visibility. *Adv Mater* 2015; **27**: 4719-4724.

14 Shen YC, Rinnerbauer V, Wang I, Stelmakh V, Joannopoulos JD *et al*. Structural colors from fano resonances. *ACS Photonics* 2015; **2**: 27-32.

15 Kumar K, Duan HG, Hegde RS, Koh SCW, Wei JN *et al*. Printing colour at the optical diffraction limit. *Nat Nanotechnol* 2012; **7**: 557-561.

16 Gu YH, Zhang L, Yang JKW, Yeo SP, Qiu CW. Color generation via subwavelength plasmonic nanostructures. *Nanoscale* 2015; **7**: 6409-6419.

17 Zi J, Yu XD, Li YZ, Hu XH, Xu C *et al*. Coloration strategies in peacock feathers. *Proc Natl Acad Sci U S A* 2003; **100**: 12576-12578.

18 Dyck J. Structure and colour-production of the blue barbs of *Agapornis roseicollis* and *Cotinga maynana*. *Z Zellforsch Mikrosk Anat* 1971; **115**: 17-29.

19 Prum RO, Torres RH, Williamson S, Dyck J. Coherent light scattering by blue feather barbs. *Nature* 1998; **396**: 28-29.

20 Liu C, Di Falco A, Molinari D, Khan Y, Ooi BS *et al.* Enhanced energy storage in chaotic optical resonators. *Nat Photonics* 2013; **7**: 473-478.

21 Coluccio ML, Gentile F, Das G, Nicastri A, Perri AM *et al.* Detection of single amino acid mutation in human breast cancer by disordered plasmonic self-similar chain. *Sci Adv* 2015; **1**: e1500487.

22 Forster JD, Noh H, Liew SF, Saranathan V, Schreck CF *et al.* Biomimetic isotropic nanostructures for structural coloration. *Adv Mater* 2010; **22**: 2939-2944.

23 Antosiewicz TJ, Apell SP, Zäch M, Zorić I, Langhammer C. Oscillatory optical response of an amorphous two-dimensional array of gold nanoparticles. *Phys Rev Lett* 2012; **109**: 247401.

24 Verre R, Antosiewicz TJ, Svedendahl M, Lodewijks K, Shegai T *et al.* Quasi-isotropic surface Plasmon polariton generation through near-field coupling to a Penrose pattern of silver nanoparticles. *ACS Nano* 2014; **8**: 9286-9294.

25 Stockman MI. Chaos and spatial correlations for dipolar eigenproblems. *Phys Rev Lett* 1997; **79**: 4562-4565.

26 Shalaev VM. *Nonlinear Optics of Random Media: Fractal Composites and Metal-Dielectric Films*. Berlin: Springer; 2013.

27 Liu C, van der Wel REC, Rotenberg N, Kuipers L, Krauss TF *et al.* Triggering extreme events at the nanoscale in photonic seas. *Nat Phys* 2015; **11**: 358-363.

28 Bauer J, Schroer A, Schwaiger R, Kraft O. Approaching theoretical strength in glassy carbon nanolattices. *Nat Mater* 2016; **15**: 438-443.

29 Hodge AM, Hayes JR, Caro JA, Biener J, Hamza AV. Characterization and mechanical behavior of nanoporous gold. *Adv Eng Mater* 2006; **8**: 853-857.

30 Mayer TM, Elam JW, George SM, Kotula PG, Goeke RS. Atomic-layer deposition of wear-resistant coatings for microelectromechanical devices. *Appl Phys Lett* 2003; **82**: 2883-2885.

31 Raney M. Method of producing finely-divided nickel: US 1628190; 1927-05-10.

32 Galinski H, Ryll T, Lin Y, Scherrer B, Evans A *et al.* Platinum-based nanowire networks with enhanced oxygen-reduction activity. *Phys Rev Appl* 2014; **2**: 054015.

33 Supansomboon S, Porkovich A, Dowd A, Arnold MD, Cortie MB. Effect of precursor stoichiometry on the morphology of nanoporous platinum sponges. *ACS Appl Mater Interfaces* 2014; **6**: 9411-9417.

34 El Mel AA, Boukli-Hacene F, Molina-Luna L, Bouts N, Chauvin A *et al.* Unusual
© 2016 Changchun Institute of Optics, Fine Mechanics and Physics (CIOMP), Chinese Academy of Sciences (CAS). All rights reserved.

1 dealloying effect in gold/copper alloy thin films: the role of defects and column boundaries in the
2 formation of nanoporous gold. *ACS Appl Mater Interfaces* 2015; **7**: 2310-2321.

3 35 Chen Q, Sieradzki K. Spontaneous evolution of bicontinuous nanostructures in
4 dealloyed Li-based systems. *Nat Mater* 2013; **12**: 1102-1106.

5 36 Qi Z, Vainio U, Kornowski A, Ritter M, Weller H *et al.* Porous gold with a nested-
6 network architecture and ultrafine structure. *Adv Funct Mater* 2015; **25**: 2530-2536.

7 37 Ashby MF. The properties of foams and lattices. *Philos Trans A Math Phys Eng Sci*
8 2006; **364**: 15-30.

9 38 Maier SA. *Plasmonics: Fundamentals and Applications*. New York: Springer; 2007.


10 39 Pendry JB, Aubry A, Smith DR, Maier SA. Transformation optics and subwavelength
11 control of light. *Science* 2012; **337**: 549-552.

12 40 Leonhardt U. Optical conformal mapping. *Science* 2006; **312**: 1777-1780.

13 41 Silveirinha M, Engheta N. Tunneling of electromagnetic energy through subwavelength
14 channels and bends using ϵ -near-zero materials. *Phys Rev Lett* 2006; **97**: 157403.

15 42 Maas R, Parsons J, Engheta N, Polman A. Experimental realization of an epsilon-
16 near-zero metamaterial at visible wavelengths. *Nat Photonics* 2013; **7**: 907-912.

17 43 Vesseur EJR, Coenen T, Caglayan H, Engheta N, Polman A. Experimental verification
18 of $n = 0$ structures for visible light. *Phys Rev Lett* 2013; **110**: 013902.

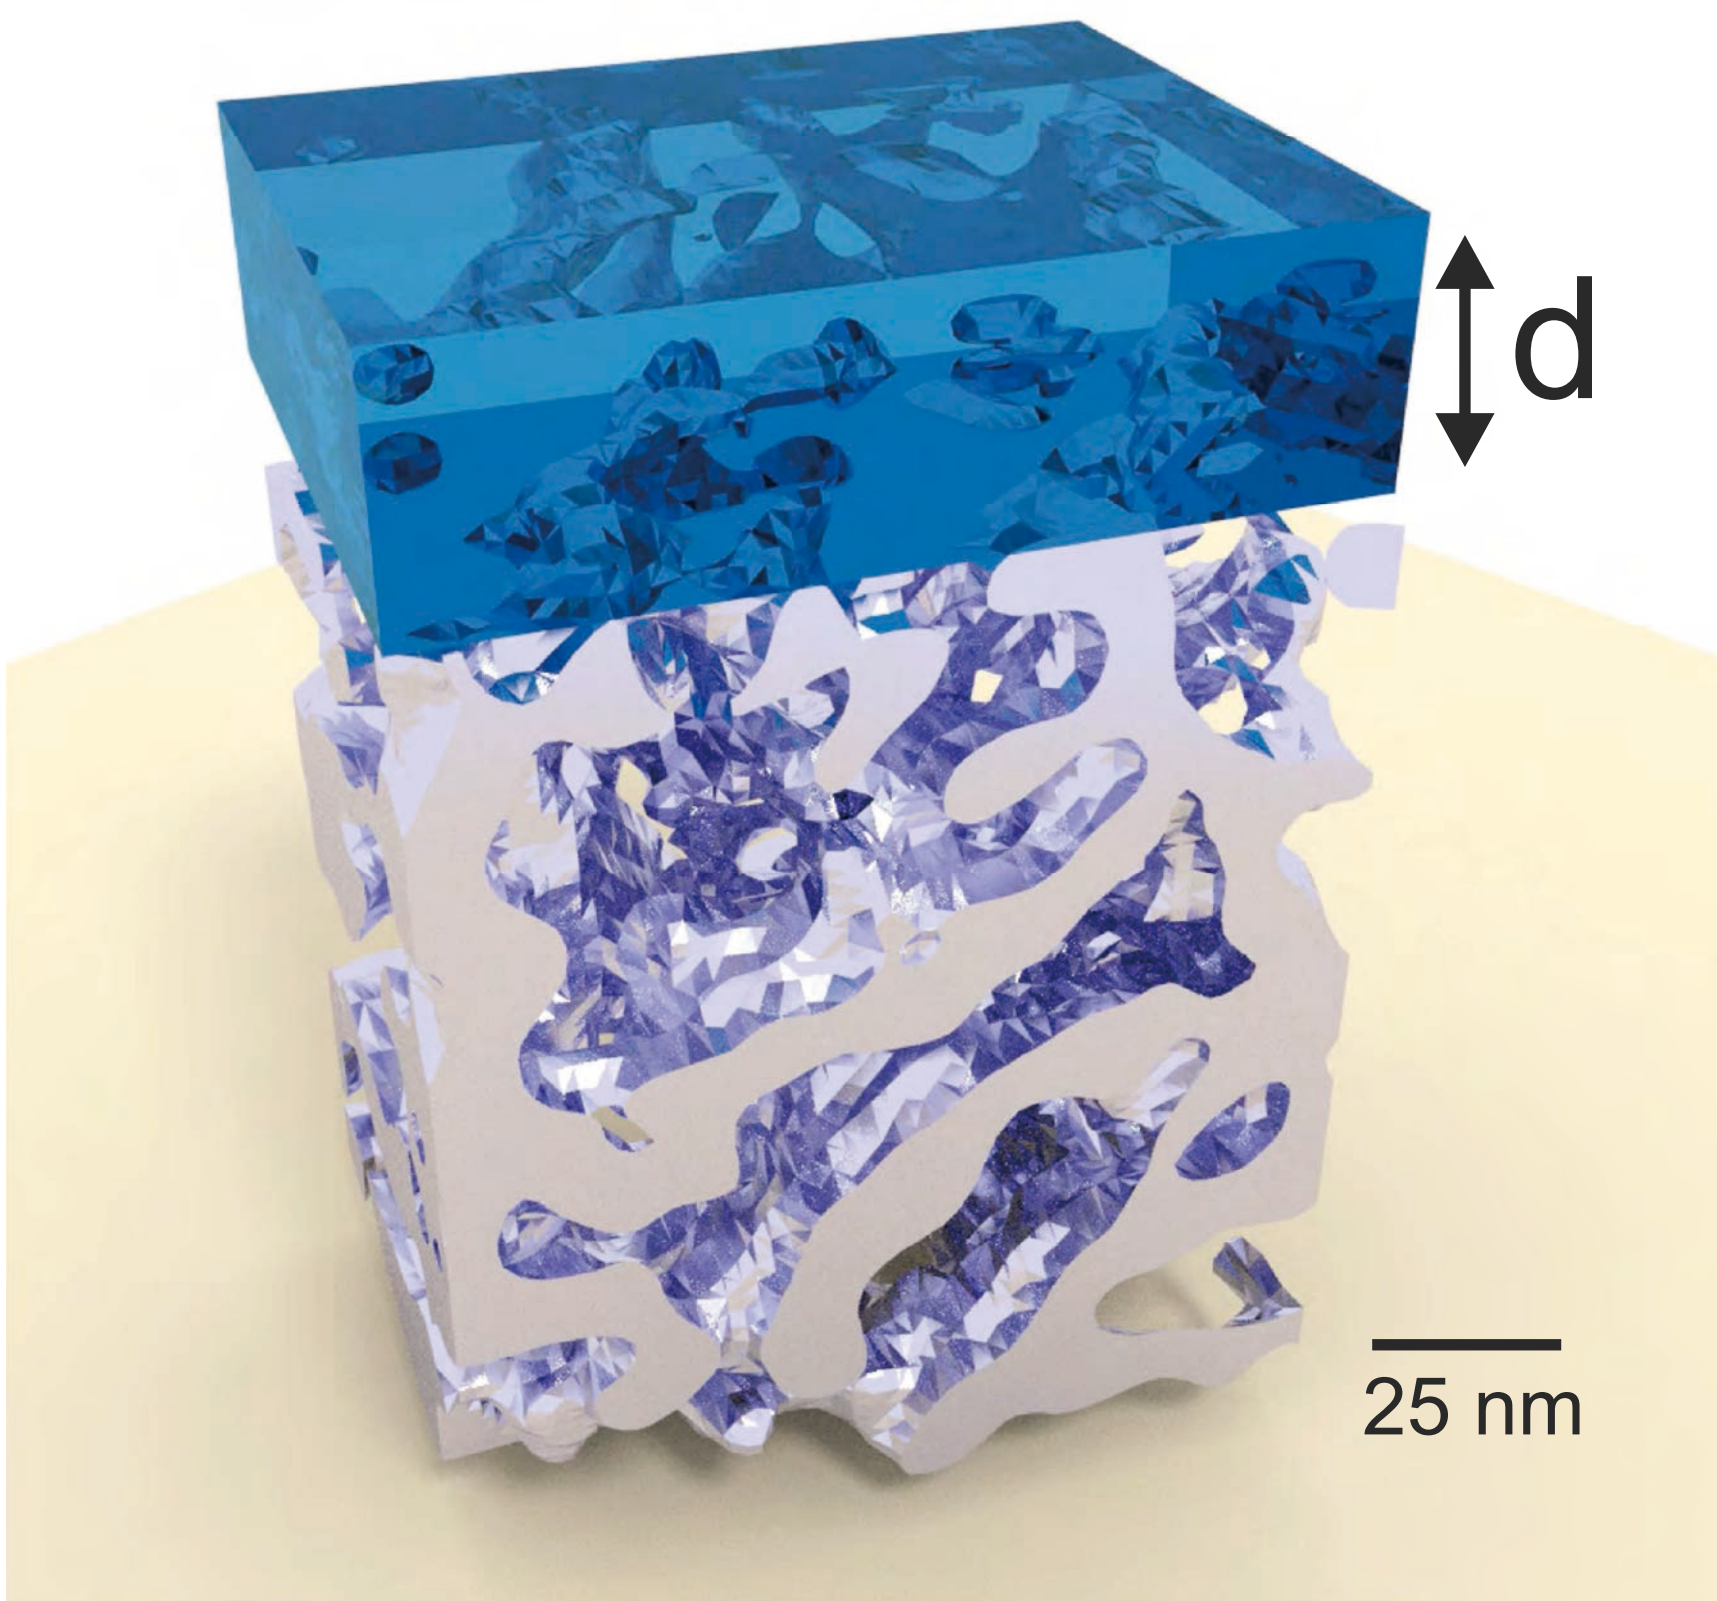
a

Pt_{0.56}Y_{0.26}Al_{0.18}


Al₂O₃

b

ACCEPTED ARTICLE PREVIEW


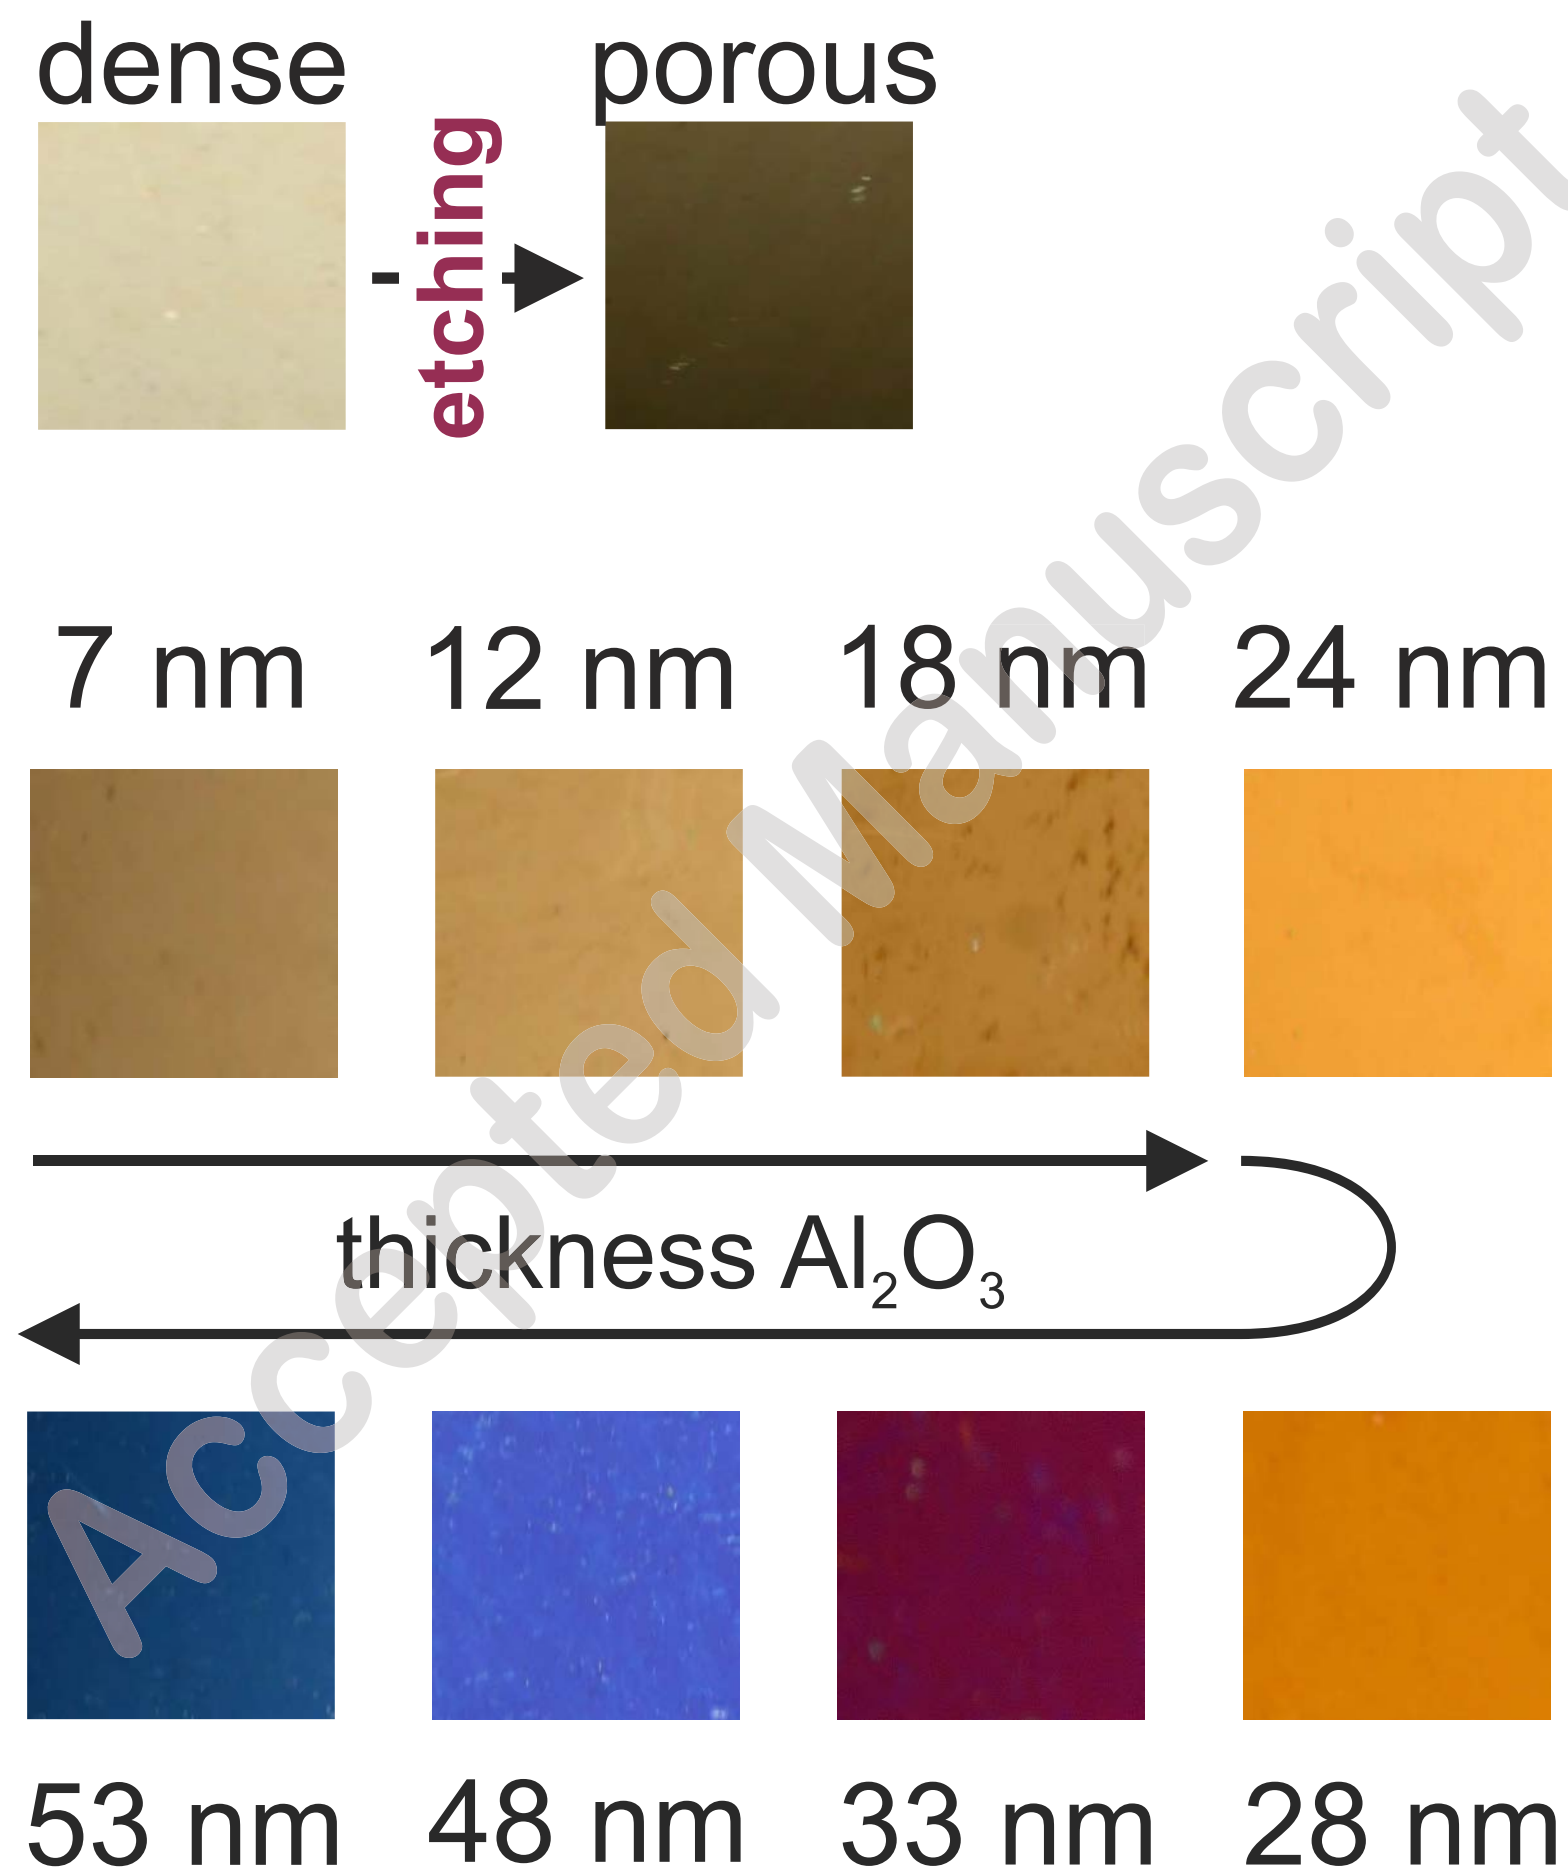



© 2016 Changchun Institute of Optics, Fine Mechanics and Physics (CIOMP), Chinese Academy of Sciences (CAS). All rights reserved.

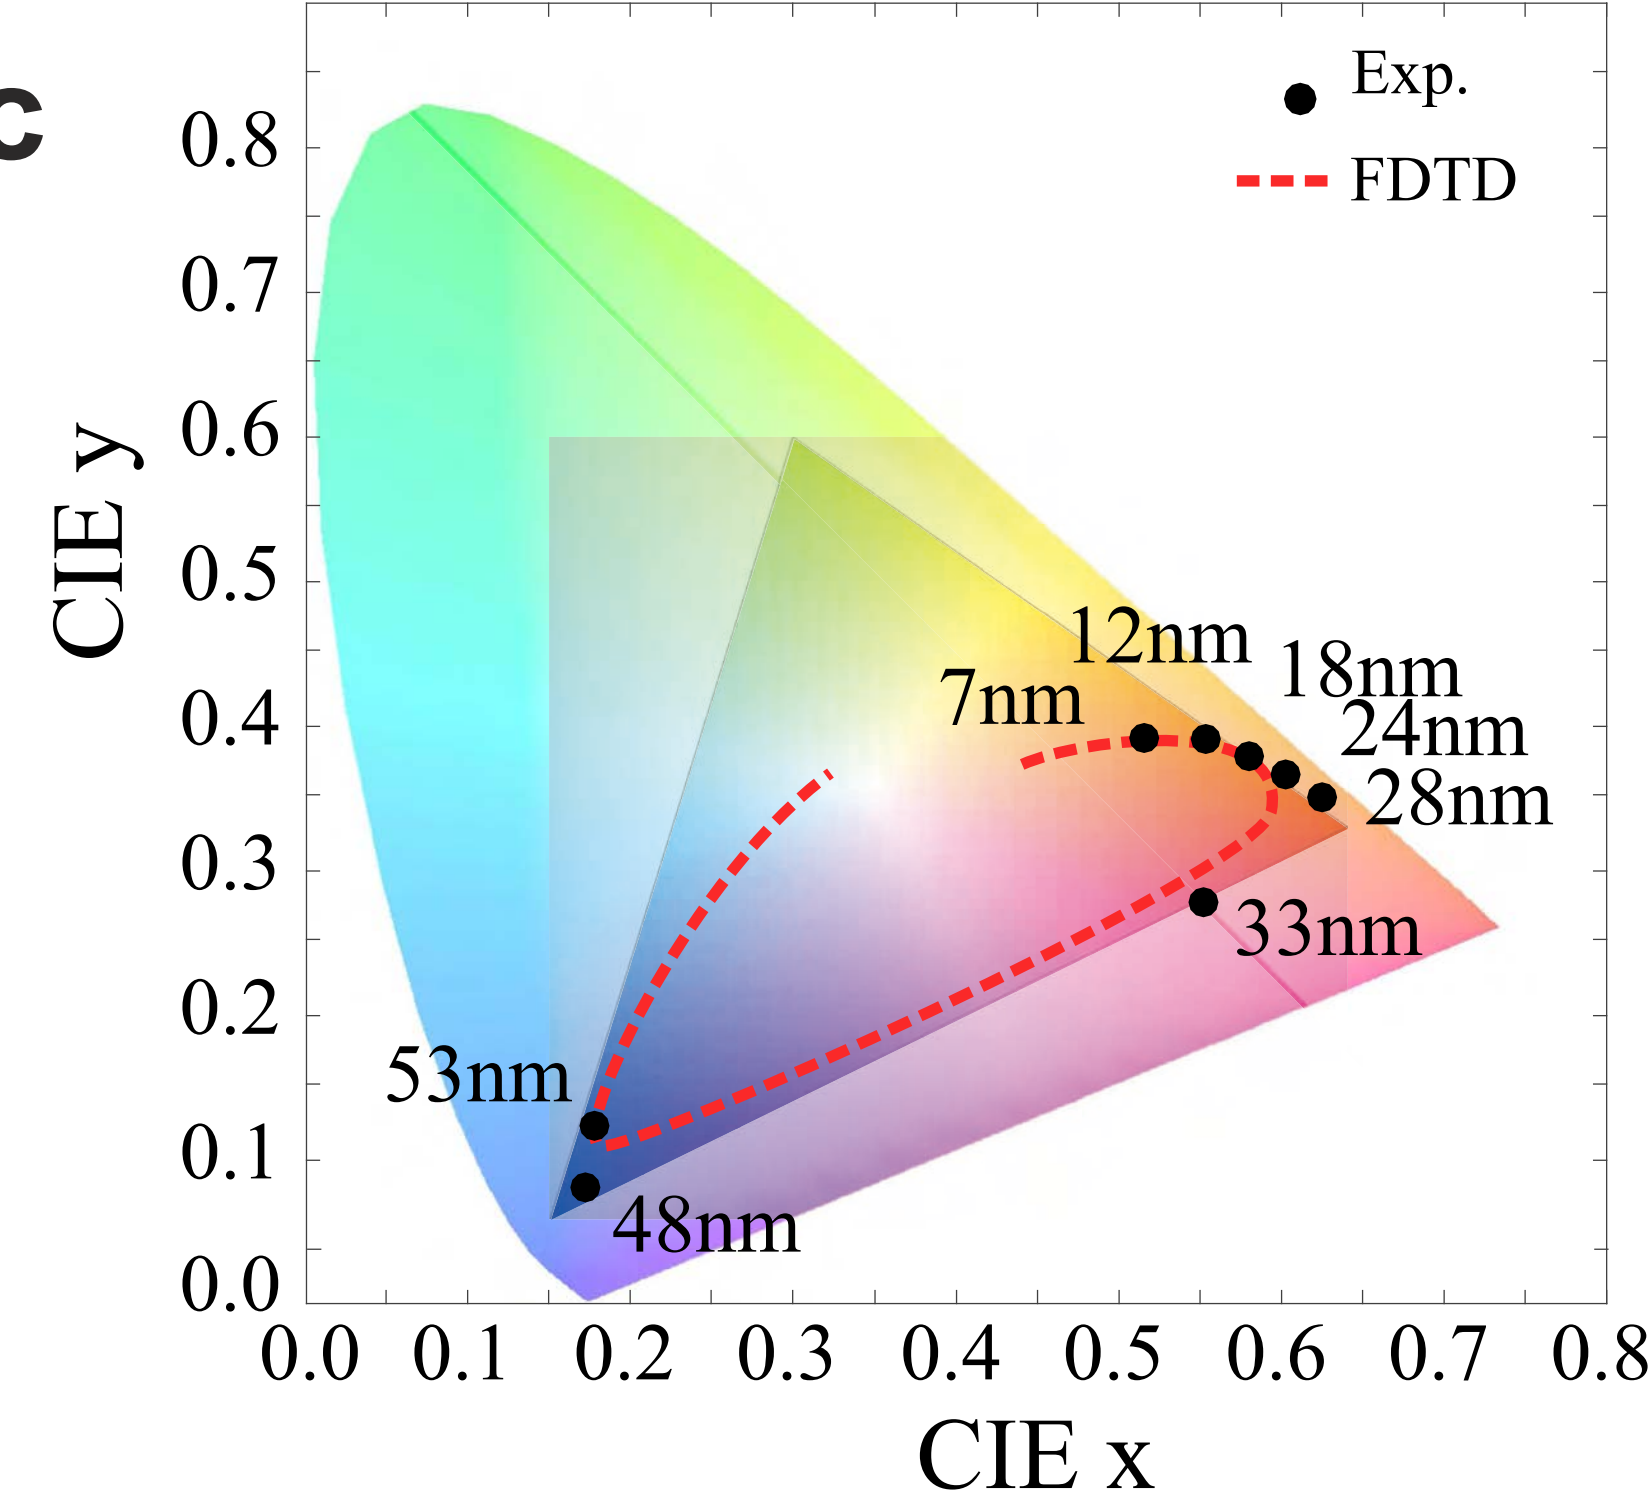c**d**



200 μm

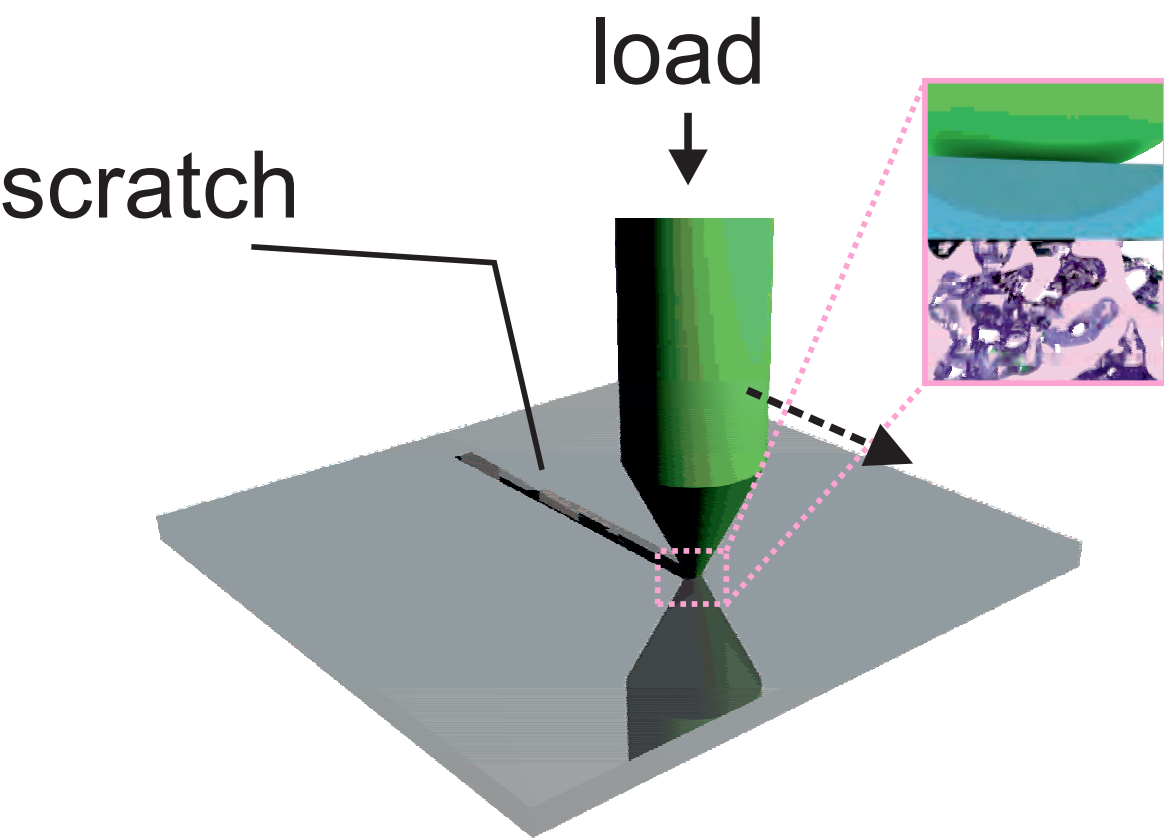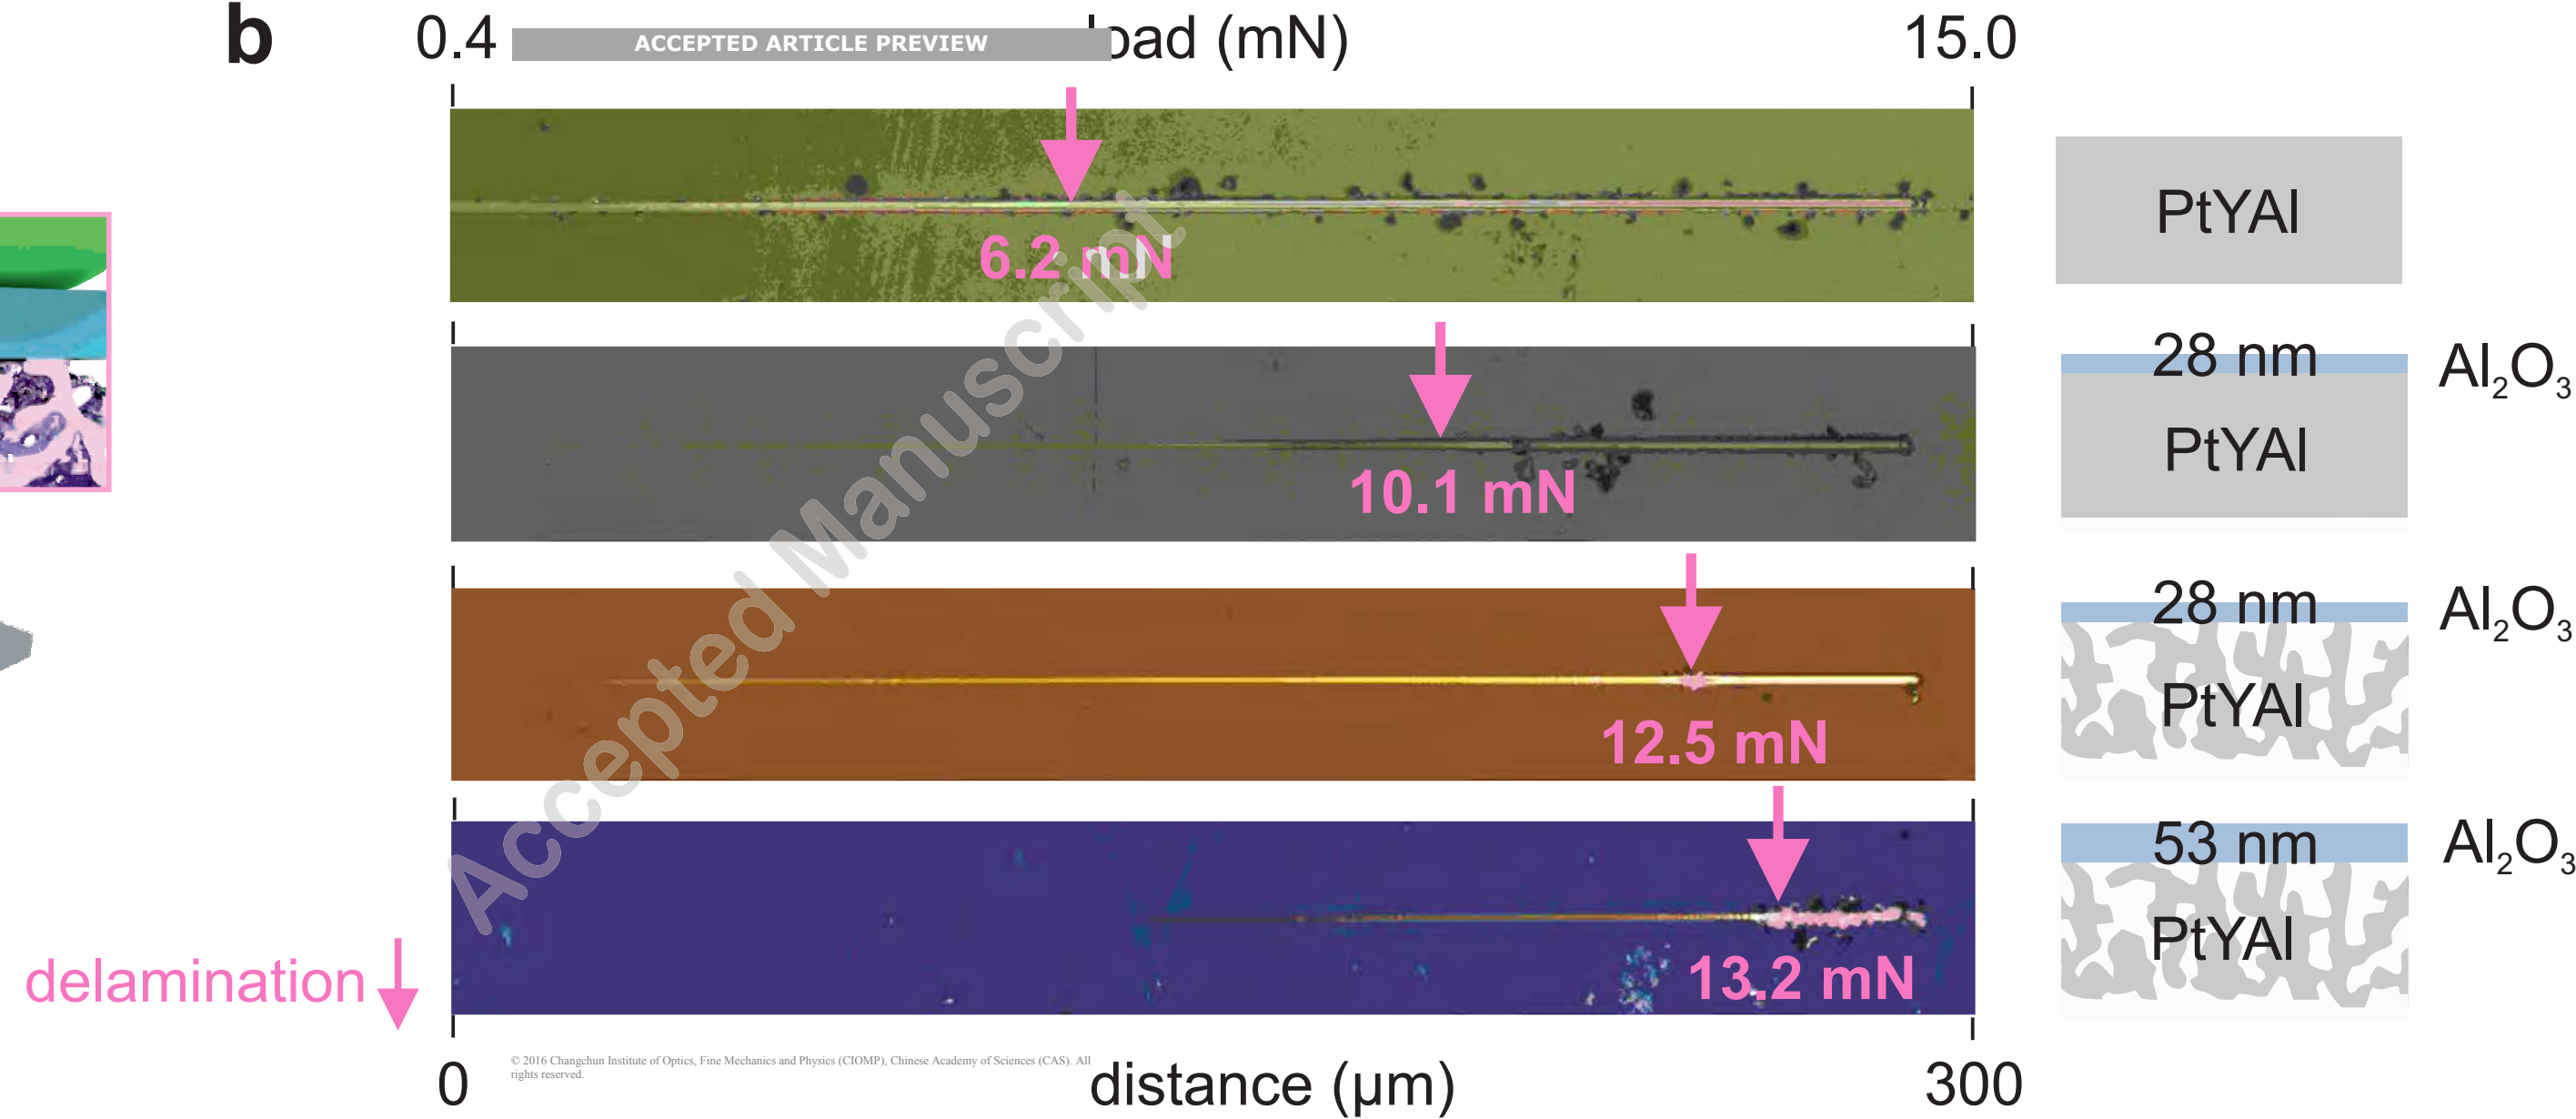
a**b**

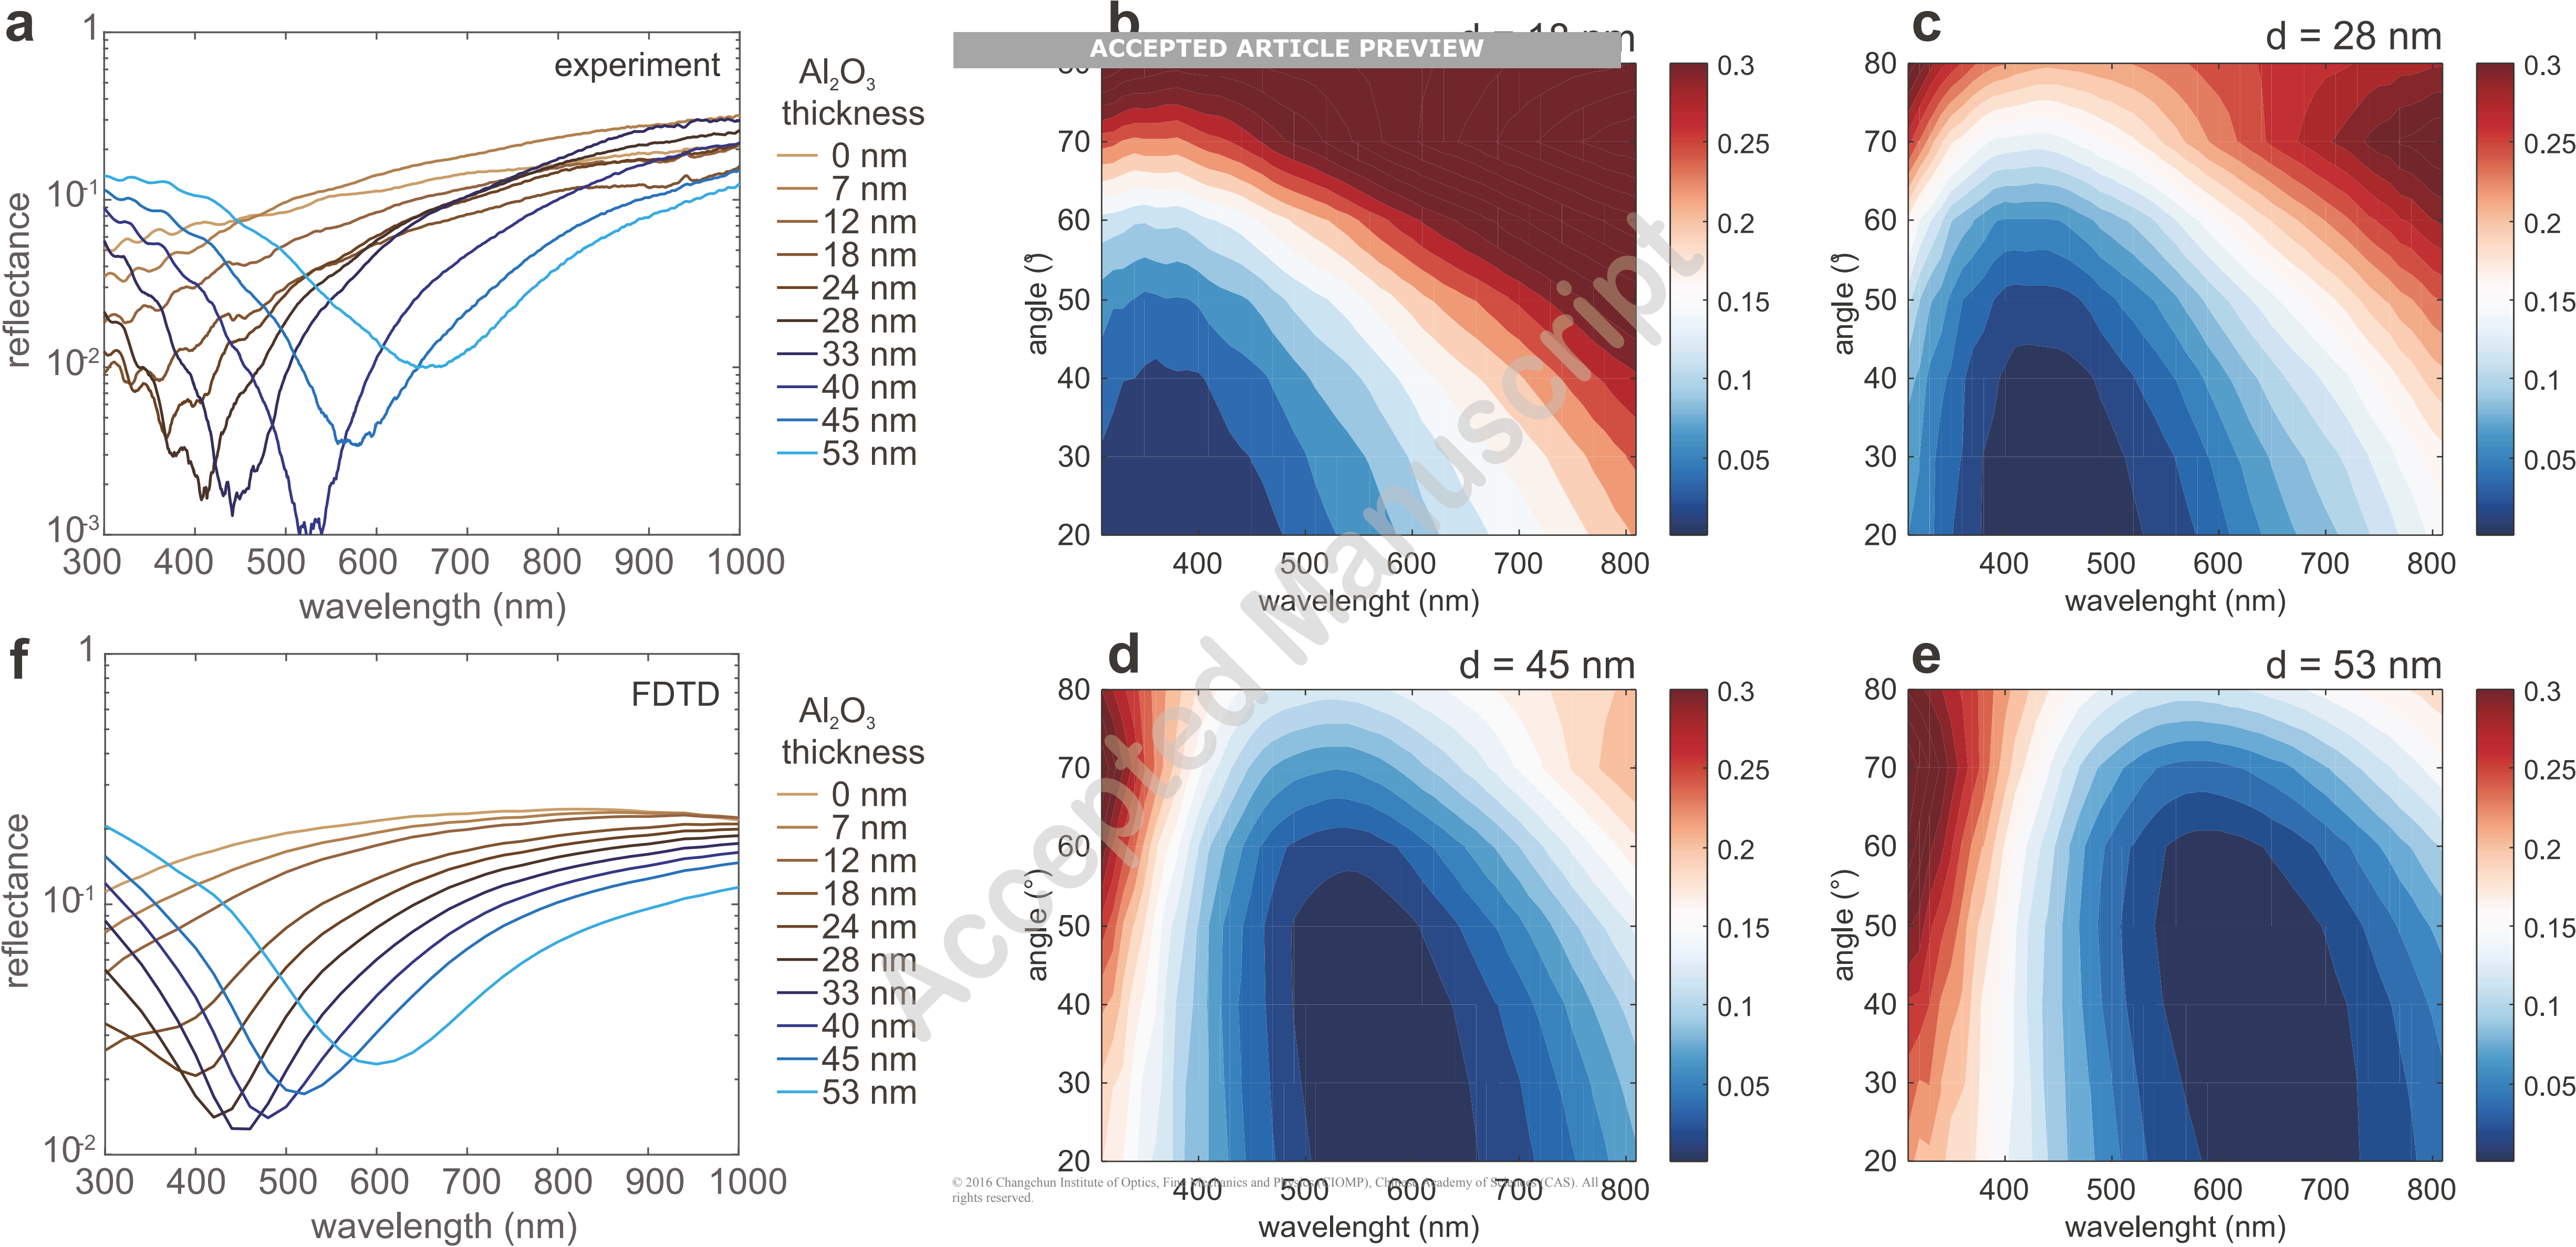


a



Original reference

ACCEPTED ARTICLE PREVIEW

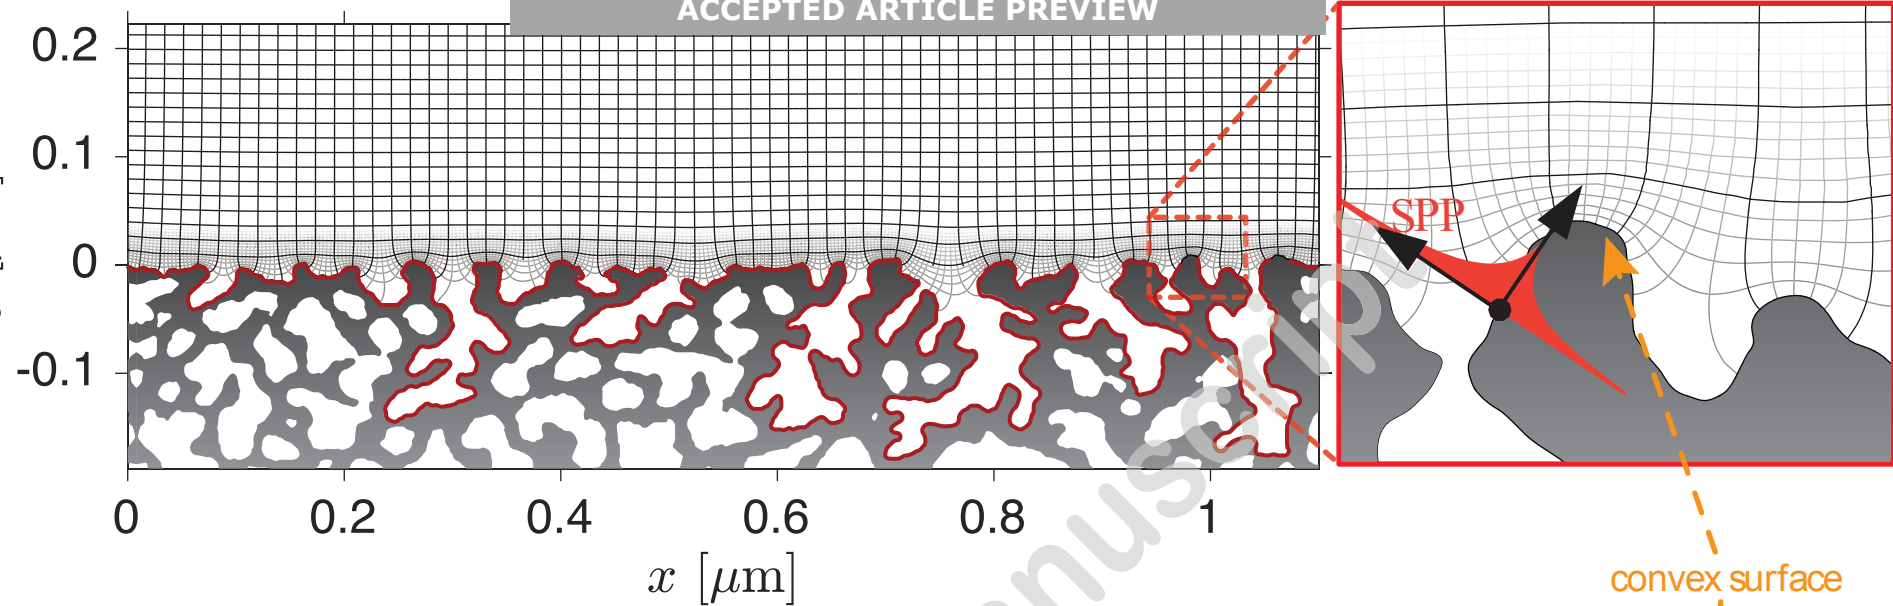**b**

Local plasmonic reference

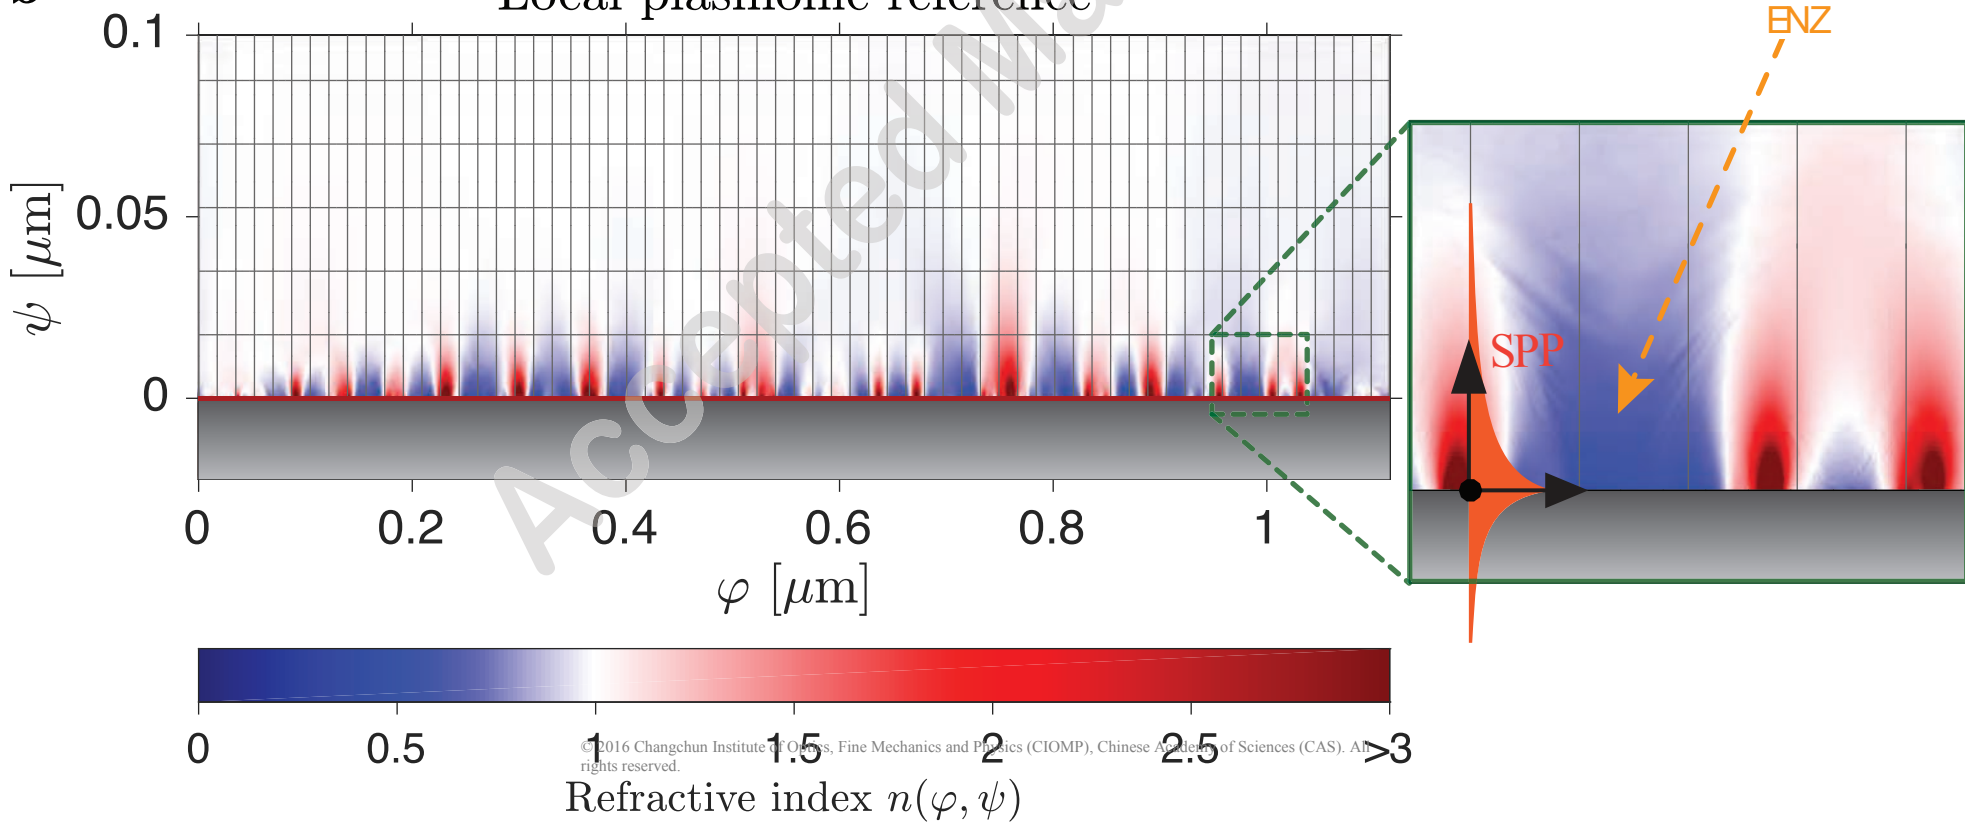

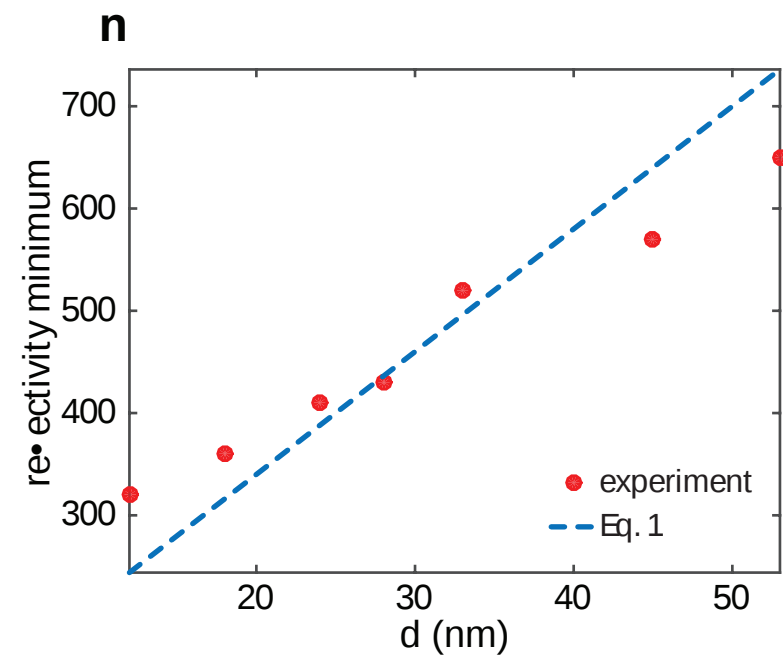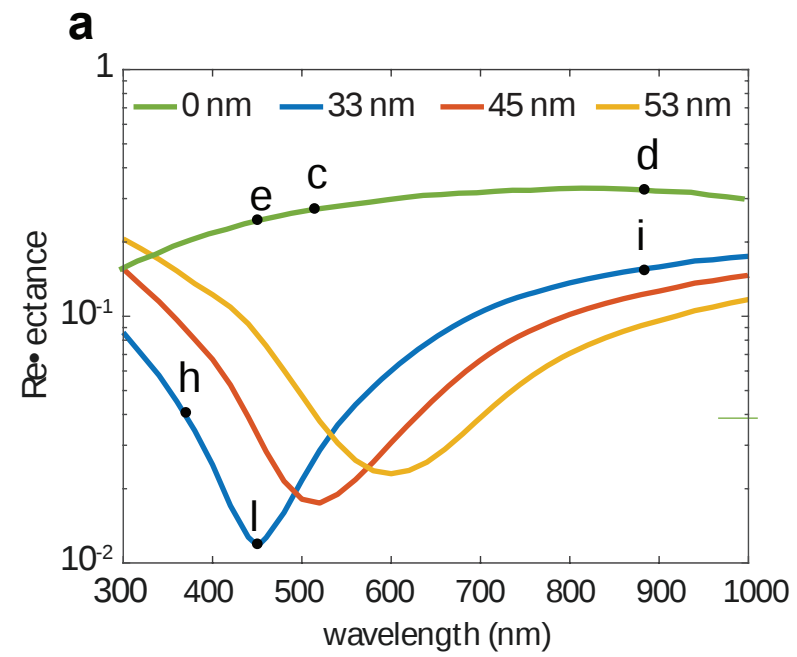

electromagnetic energy (a.u.)

